

WOVEN MULTI-DIRECTIONAL COMPOSITE: MODE I FATIGUE DELAMINATION PROPAGATION

L. Banks-Sills and I. Simon

School of Mechanical Engineering, Tel Aviv University, Ramat Aviv, Israel

Double cantilever beam (DCB) specimens fabricated from 15 plies of a plain woven prepreg (G0814/913) arranged in a multi-directional (MD) layout were tested by means of constant amplitude fatigue cycles under displacement control. The prepreg consists of carbon fibers in an epoxy matrix. The plies were stacked in a multi-directional arrangement in which each ply was rotated by 45^0 in the ply plane with respect to each adjacent ply. Eight specimens were tested. Four different displacement cyclic ratios R_d were used, where

$$R_d = \frac{d_{min}}{d_{max}} \quad (1)$$

with d_{min} and d_{max} are the minimum and maximum displacements in a fatigue cycle. These included 0.1, 0.33, 0.5 and 0.75. It may be noted that the tests were carried out with frequencies between 4 and 6 Hz, many of them running continuously up to 3,000,000 cycles.

The delamination propagation rate da/dN was calculated from the experimental data and plotted using a modified Paris law with different functions of the mode I energy release rate \hat{G}_I . In Fig. 1a, results of the delamination propagation rate da/dN are plotted vs the range of the effective energy release rate given by

$$\Delta \hat{G}_{Ieff} = \left(\sqrt{\hat{G}_{I_{max}}} - \sqrt{\hat{G}_{I_{min}}} \right)^2 \quad (2)$$

where $\hat{G}_{I_{max}}$ and $\hat{G}_{I_{min}}$ are, respectively, the maximum and minimum values of the mode I energy release rate which has been normalized with respect to the fracture toughness. It may be observed in Fig. 1a that there is a good correspondence between results obtained with the same R_d -ratio. Moreover, the delamination propagation rate increases as the R_d -ratio increases for a given value of $\Delta \hat{G}_{Ieff}$. Using a different parameter, it is possible to obtain a master curve for all R_d -ratios. Define

$$\Delta \bar{\mathcal{K}}_I = \frac{\sqrt{\hat{G}_{I_{max}}} - \sqrt{\hat{G}_{I_{thr}}}}{\sqrt{1 - \sqrt{\hat{G}_{I_{max}}}}} \quad (3)$$

where $\hat{G}_{I_{thr}}$ is the normalized value of the threshold energy release rate. Using the parameter in eq. (3), it may be observed in Fig. 1b that the eight curves for different R_d -ratios unify into one master curve.

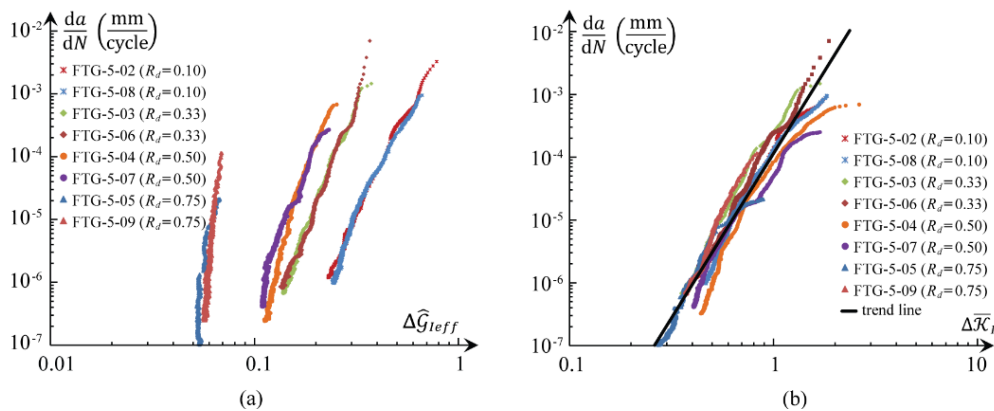


Figure 1. Delamination propagation rate as a function of (a) $\Delta \hat{G}_{Ieff}$ and (b) $\Delta \bar{\mathcal{K}}_I$.